

# Ultrasonic testing of steel flat product of thickness equal or greater than 6 mm (reflection method)

The European Standard EN 10160:1999 has the status of a  
British Standard

ICS 77.140.50

## National foreword

This British Standard is the English language version of EN 10160:1999. It supersedes BS 5996:1993, which is withdrawn.

The UK participation in its preparation was entrusted by Technical Committee ISE/73, Steels for pressure purposes, to Subcommittee ISE/73/2, Steel plates and bars for pressure purposes, which has the responsibility to:

- aid enquirers to understand the text;
- present to the responsible European committee any enquiries on the interpretation, or proposals for change, and keep the UK interests informed;
- monitor related international and European developments and promulgate them in the UK.

A list of organizations represented on this subcommittee can be obtained on request to its secretary.

### Cross-references

The British Standards which implement international or European publications referred to in this document may be found in the BSI Standards Catalogue under the section entitled "International Standards Correspondence Index", or by using the "Find" facility of the BSI Standards Electronic Catalogue.

A British Standard does not purport to include all the necessary provisions of a contract. Users of British Standards are responsible for their correct application.

**Compliance with a British Standard does not of itself confer immunity from legal obligations.**

### Summary of pages

This document comprises a front cover, an inside front cover, the EN title page, pages 2 to 14, an inside back cover and a back cover.

The BSI copyright notice displayed throughout this document indicates when the document was last issued.

This British Standard, having been prepared under the direction of the Engineering Sector Committee, was published under the authority of the Standards Committee and comes into effect on 15 November 1999

### Amendments issued since publication

Amd. No.	Date	Comments

EUROPEAN STANDARD  
NORME EUROPÉENNE  
EUROPÄISCHE NORM

**EN 10160**

July 1999

ICS 77.040.20; 77.140.50

English version

**Ultrasonic testing of steel flat product of thickness equal or  
greater than 6 mm (reflection method)**

Contrôle ultrasonore des produits plats en acier d'épaisseur  
égale ou supérieure à 6 mm (méthode par réflexion)

Ultraschallprüfung von Flacherzeugnissen aus Stahl mit  
einer Dicke größer oder gleich 6 mm (Reflexionsverfahren)

This European Standard was approved by CEN on 3 March 1999.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

**CEN**

EUROPEAN COMMITTEE FOR STANDARDIZATION  
COMITÉ EUROPÉEN DE NORMALISATION  
EUROPÄISCHES KOMITEE FÜR NORMUNG

Central Secretariat: rue de Stassart, 36 B-1050 Brussels

## Contents

<b>Foreword</b> .....	<b>2</b>
1 <b>Scope</b> .....	3
2 <b>Normative references</b> .....	3
3 <b>Terms and definitions</b> .....	3
4 <b>Principle</b> .....	4
5 <b>Personnel</b> .....	4
6 <b>Apparatus</b> .....	4
7 <b>Coupling conditions - Surface condition of the flat product</b> .....	6
8 <b>Scanning plan</b> .....	6
9 <b>Procedure</b> .....	8
10 <b>Acceptance criteria</b> .....	9
11 <b>Test report</b> .....	10
Annex A (informative) <b>List of equivalent terms in several European languages</b> .....	14

## Foreword

This European Standard has been prepared by Technical Committee ECISS/TC 2 "Steel physico-chemical and non-destructive testing", the Secretariat of which is held by AFNOR.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by January 2000, and conflicting national standards shall be withdrawn at the latest by January 2000.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

## 1 Scope

This European Standard describes a method for the ultrasonic testing of uncoated flat steel product for internal discontinuities. It is applicable to flat product in nominal thickness range of 6 mm to 200 mm of non-alloyed or alloyed steel, excluding austenitic or austenoferritic steels. However, this standard may be applied to the latter types of steels provided that the difference between the amplitude of the noise signal and that of the echo detection threshold is sufficient for the limit fixed.

This standard also defines four quality classes for the flat product body (classes S<sub>0</sub>, S<sub>1</sub>, S<sub>2</sub> and S<sub>3</sub>) and 5 classes (E<sub>0</sub>, E<sub>1</sub>, E<sub>2</sub>, E<sub>3</sub>, E<sub>4</sub>) for the edges in accordance with the criteria specified in clause 9.

Other methods of testing (e.g. by transmission) or other test equipment may be used at the manufacturer's discretion provided that they give identical results to those obtained under the conditions of this standard. In the event of a dispute, only the method defined in this standard shall prevail.

Testing of flat product of thickness less than 6 mm may be the subject of special agreements between the parties concerned.

The inspection is normally carried out in the place of production or on the premises of the supplier. If specified on the order, the inspection may take place in the presence of the purchaser or his representative<sup>1)</sup>.

A list of equivalent terms in several European languages is given in annex A.

## 2 Normative references

This European Standard incorporates by dated or undated reference, provisions from other publications. These normative references are cited at the appropriate places in the text and the publications are listed hereafter. For dated references, subsequent amendments to or revisions of any of these publications apply to this European Standard only when incorporated in it by amendment or revision. For undated references the latest edition of the publication referred to applies.

EN 473, *Qualification and certification of NDT personnel - General principles*

prEN 1330-4, *Non destructive testing - Terminology - Part 4 : Terms used in ultrasoning testing*

## 3 Terms and definitions

For the purposes of this European Standard, the definitions given in prEN 1330-4 and the following definitions apply:

### 3.1

#### **internal discontinuity**

any imperfection lying within the thickness of the flat product, e.g. planar or laminar imperfection, single-plane or multi-plane inclusion bands or clusters

NOTE It is referred in the text as discontinuity.

### 3.2

#### **defect**

unacceptable internal discontinuity, i.e. exceeding the specified maximum size or population density limits

---

<sup>1)</sup> In this case, all steps should be taken to ensure that the production process is not disturbed.

### 3.3

#### **population density**

the number of individual internal discontinuities of a size greater than a specified minimum size and less than a specified maximum size per specified area of body or length of edge zone

### 3.4

#### **manual and assisted manual testing**

testing by an operator applying an ultrasonic probe, or probes, to the flat product surface, manually executing the appropriate scanning pattern on the flat product surface and visually assessing ultrasonic signal indications on the electronic equipment screen either by direct viewing or by built-in signal amplitude alarm devices

### 3.5

#### **automatic and semi-automatic testing**

testing using a mechanized means of applying the ultrasonic probe or probes to, and executing the appropriate scanning pattern on the flat product surface, together with ultrasonic signal indication evaluation by electronic means. Such testing can be either fully automatic with no operator involvement, or semi-automatic when the operator performs basic equipment operation functions

## **4 Principle**

The method used is based on the reflection of ultrasonic waves (generally longitudinal), the mean direction of which is perpendicular to the surface of the product. The examination consists of:

- a) locating any discontinuity by comparing the amplitude of the discontinuity echo with the amplitude of the echo of a flat-bottomed hole of a given diameter and located at the same depth as the discontinuity.

NOTE Only those discontinuities giving an echo at least equivalent in amplitude to that of the echo obtained with the reference flat-bottomed hole are taken into consideration;

- b) then determining its area, the contour of the discontinuity being defined by the positions of the centre of the probe corresponding to an echo amplitude of half the maximum amplitude of the discontinuity under consideration (6 dB method).

The examination is carried out during the first ultrasonic scan for all the flat product thicknesses and from one side only.

## **5 Personnel**

Testing is carried out by qualified personnel under the responsibility of a level 3 individual certified in accordance with EN 473.

## **6 Apparatus**

### **6.1 Description**

The detection apparatus shall be equipped with an oscilloscope screen allowing the path of the ultrasonic waves in the flat product to be followed. The oscillograms shall be clearly visible, the peaks corresponding to the successive echoes being sharp and very clear; the apparatus shall be suitably calibrated and shall be equipped with an amplifier marked in decibels.

Both ultrasonic testing apparatus with display monitor and amplifier control graduated in dB, or apparatus without display monitor can be used. Apparatus without display monitor shall be able to carry out automatic amplitude testing and evaluation and their unit of measurement shall be calibrated in dB.

It shall be possible to regulate amplification, power and time base.

The apparatus includes at least one probe which may be either a probe with a single transducer serving for both emission and reception (single probe) or a double transducer probe (separate emission-reception transducers). The mean direction of the waves emitted and received shall be perpendicular to the surface of the product.

The probe shall have a frequency and dimensions such that the required sensitivity can be guaranteed throughout the extent of the test field.

The single probes shall be such that their dead zone is as small as possible, i.e. 15% of the flat product thickness or 15 mm whichever is the smaller. The focusing zone of the double transducer probes shall be adapted to the thickness of the flat product.

The main dimensions of probes are 10 mm to 25 mm in diameter and the probes shall have a nominal frequency in the range of 2 MHz to 5 MHz. Probes of larger dimension and of a nominal frequency that is outside the range of 2 MHz to 5 MHz may be used for automatic or semi-automatic testing and/or when the flat product exhibits high attenuation provided that the main requirements of this standard are met.

The type of the probe depends on the thickness of the flat product as given in Table 1:

Table 1 — Type of probe

Nominal thickness of the flat product (e) or depth of any discontinuity zone mm	Type of probe
$6 \leq e < 60$	Double transducer probe
$60 \leq e \leq 200$	Single or double transducer probe a) b)

a) In the event of a dispute, the type of probe to be used shall be the subject of an agreement.  
b) Where automatic testing is carried out using immersion or water column techniques, it is permissible to use single crystal probes < 60 mm thick.

The probe may be either hand held, or mounted on a continuous testing apparatus with a scanning speed sufficiently low for the discontinuities to be easily located taking into account the display delay of the screen, or fitted with a device which indicates the discontinuity.

When double transducer probes are used, the orientation of the barrier separating the two transducers shall be perpendicular to the scanning direction.

The verification of the apparatus shall be carried out in accordance with the relevant national standards.

## 6.2 Adjustment of the apparatus

Adjustment of the apparatus for use particularly requires that the time base, power and amplification be determined.

The time base is adjusted to a value at which the distance, on the oscilloscope screen, between the emission echo and back-wall echo is sufficient to allow a defect echo to be clearly detected between them.

At least two back-wall echoes should be displayed.

The power and amplification are adjusted in conjunction on a sound area which does not give any discontinuity echo. The first back-wall echo shall then be brought up to the maximum amplitude compatible with the height of the screen in the field of linearity of the apparatus (generally between 80% and 100% full screen height).

The system shall be checked at least once every 8 h.

## **7 Coupling conditions - Surface condition of the flat product**

The coupling medium shall ensure an adequate contact between the probe and the surface of the flat product. Water is normally used but other coupling media (e.g. oil, paste) may be used at the discretion of the supplier.

The surface condition shall permit at least two successive back-wall echoes to be distinguished when the probe is placed on any area free from internal discontinuities. The flat products are normally examined without any special preparation of the surface.

## **8 Scanning plan**

### **8.1 General**

For the flat product body, the testing is based on statistical methods, unless otherwise specified in the order.

According to the quality class, scanning of the flat product shall be carried out in accordance with **8.2** and/or **8.3**.

By agreement at the time of order, a scanning with a defined scan coverage or a scanning of all body part of the flat product may be provided, the operating conditions being included in the agreement.

### **8.2 Testing of the flat product body**

#### **8.2.1 Class S<sub>0</sub> and S<sub>1</sub> flat product**

Scanning comprises continuous examination along the lines of a grid made of a 200 mm square parallel to the edges of the flat product, or along parallel or oscillating lines distributed uniformly over the area, giving the same degree of control.

#### **8.2.2 Class S<sub>2</sub> and S<sub>3</sub> flat product**

Scanning comprises continuous examination along the lines of a grid made of a 100 mm square parallel to the edges of the flat product, or along parallel or oscillating lines distributed uniformly over the area, giving the same degree of control.

### 8.3 Testing of the flat product edges

Scanning comprises a full examination of a zone in accordance with Table 2 over the four edges of the flat product.

**Table 2 — Zone width for flat product edges**

<b>Thickness of the flat product e mm</b>	<b>Zone width mm</b>
$6 \leq e < 50$	50
$50 \leq e < 100$	75
$100 \leq e \leq 200$	100

## 9 Procedure

### 9.1 Sensitivity and range setting

For each type of probe, curves shall be used giving:

- a) the change in the amplitude of the back-wall echo as a function of the thickness of the flat product;
- b) the change in the amplitude of the echo of the flat-bottomed hole as a function of its depth, for holes of diameter:
  - 11 mm for classes S<sub>0</sub>, S<sub>1</sub>, E<sub>0</sub> and E<sub>1</sub>;
  - 8 mm for classes S<sub>2</sub>, E<sub>2</sub> and E<sub>3</sub>;
  - 5 mm for classes S<sub>3</sub> and E<sub>4</sub>.

The bottom of the hole shall be as flat as practicable, parallel to the ultrasound entry surface and free from pits or score marks that significantly degrade its ultrasonic reflectivity. The tolerance on the diameter of the flat bottomed hole or width of recess shall be + 5%.

The use of rectangular recesses is permitted provided that the length and width of the recess are chosen to provide an ultrasonic signal response essentially equivalent to that obtained from the stipulated flat bottomed hole using the same equipment/transducer type combination.

When testing with a double-transducer probe, only the 5 mm diameter hole is used for all the qualities as the characteristic curves corresponding to the 8 mm and 11 mm diameter holes become confused with the curve of the back-wall echo.

These curves shall be determined using blocks (graduated block for the curve showing the variation in the amplitude of the back-wall echo and blocks comprising the flat-bottomed holes at different depths for the characteristic curves for 11 mm, 8 mm and 5 mm diameters). The blocks are made of carbon steel with a homogenous structure and each curve shall be determined from at least five points distributed over the entire field of use of the probe. All these curves can be supplied by the manufacturer of the probe.

Thus, for a flat product of given thickness, the method consists of adjusting the amplitude of the back-wall echo to the value given by the curve for the variation of the back-wall echo amplitude and comparing the amplitude of the discontinuity echo with the characteristics curves (for 11 mm, 8 mm and 5 mm diameters) in accordance with the class selected. Only discontinuities for which the amplitude of the echo is greater than that of the characteristic curve shall be taken into account.

### 9.2 Determination of the area of discontinuities

#### 9.2.1 Testing the flat product body

##### 9.2.1.1 Testing with double transducer probes

The area of all the discontinuities giving responses that exceeded the characteristic curve shall be determined using the 6 dB technique, i.e. the contour of the discontinuity being defined as the positions of the centre of the probe when the response from the discontinuity is equal to half the maximum amplitude. A rectangle that encompasses the whole of the discontinuity is then determined, the major dimension of which is called the length of the discontinuity and the minor dimension the width of the discontinuity. The area of the rectangle is also calculated.

The area of the rectangle defines the area S of the discontinuity. Two nearby discontinuities shall be considered to represent a single discontinuity, the area being equal to the sum of the two if the distance between them is less than or equal to the length of the smaller of the two.

### 9.2.1.2 Testing with single probes

The test consists of :

- a) for class  $S_0$  and  $S_1$  flat product : determination of the area in accordance with the method defined in 8.2.1.1;
- b) for class  $S_2$  and  $S_3$  flat product : simply counting of the discontinuities which can be done when they are detected using the characteristic curves for 5 mm, 8 mm and 11 mm diameter holes.

The following is thus determined:

- for class  $S_2$  : the number of discontinuities giving echoes with an amplitude greater than the 11 mm diameter curve and the number  $N_2$  of discontinuities (Table 4) giving echoes with an amplitude between characteristic curves for the 8 mm and 11 mm diameter holes;
- for class  $S_3$  : the number of discontinuities giving echoes with an amplitude greater than the 8 mm diameter curve and the number  $N_3$  of discontinuities (Table 4) giving echoes with an amplitude between characteristic curves for the 5 mm and 8 mm diameter holes.

### 9.2.2 Testing the edges

The test consists of scanning the total area of the edges (or areas to be welded according to sketches) where discontinuities were located defined in 8.3 under the same conditions as for flat product body (9.2.1).

The following are determined:

- the maximum dimension ( $L_{max}$ ) and minimum dimension ( $L_{min}$ ) of the discontinuity in the direction parallel to the edge of the flat product;
- the area (S) of the discontinuity;
- the number of discontinuities smaller than the maximum area ( $S_{max}$ ) and longer than minimum dimension ( $L_{min}$ ) per 1m length.

The determination of these properties of the discontinuity is obtained using the 6 dB method.

## 10 Acceptance criteria

Tables 3 and 4 give the acceptance criteria for the four quality classes ( $S_0$ ,  $S_1$ ,  $S_2$ ,  $S_3$ ) for the flat product body, depending on the type of probe used and the Table 5 for the five edge classes ( $E_0$ ,  $E_1$ ,  $E_2$ ,  $E_3$ ,  $E_4$ ) (see Figure 1).

Subject to agreement on ordering, the flat product may be supplied with different quality classes for flat product body and/or edges.

## 11 Test report

When requested, the manufacturer shall submit a test report which shall include at least the following points:

- a) reference to the present European Standard;
- b) reference data of the flat product examined (identification of the grade, heat treatment condition, surface condition, dimensions);
- c) the characteristics of the ultrasonic probe (type, dimensions, frequency) and of the apparatus;
- d) the operation conditions (coupling medium, scanning, method of area determination used, setting of the apparatus);
- e) the test results;
- f) a list of special points which have been the subject of special agreement;
- g) date of test report.

**Table 3 — Acceptance criteria for testing with double transducer probes  
for the body of flat products for thicknesses < 60 mm**

Class	Unacceptable individual discontinuity mm <sup>2</sup>	Acceptable clusters of discontinuities	
		Area a) considered mm <sup>2</sup>	Maximum density not greater than
S <sub>0</sub>	S > 5 000	1 000 < S ≤ 5 000	20 in the most populated 1 m x 1 m square
S <sub>1</sub>	S > 1 000	100 < S ≤ 1 000	15 in the most populated 1 m x 1 m square
S <sub>2</sub>	S > 100	50 < S ≤ 100	10 in the most populated 1 m x 1 m square
S <sub>3</sub>	S > 50	20 < S ≤ 50	10 in the most populated 1 m x 1 m square

a) Area of each discontinuity in the cluster in question (see 9.2).

NOTE This table can be used for thicknesses ≥ 60 mm if an appropriate method other than the 6 dB method is used for the sizing of discontinuities.

Table 4 — Acceptance criteria for testing with normal probes for the body of flat products

Class	Unacceptable individual discontinuity	Acceptable clusters of discontinuities	
		Dimensions <sup>a)</sup> (number) considered	Maximum number not greater than
$S_0$	$S > 5\ 000\ mm^2$	$1\ 000 < S \leq 5\ 000\ mm^2$	20 in the most populated $1\ m \times 1\ m$ square
$S_1$	$S > 1\ 000\ mm^2$	$100 < S \leq 1\ 000\ mm^2$	15 in the most populated $1\ m \times 1\ m$ square
$S_2$	Discontinuities where the flaw echo has an amplitude greater than the characteristic curve $\varnothing 11\ mm$	$N_2$ (between $\varnothing 8\ mm$ and $\varnothing 11\ mm$ )	10 in the most populated $1\ m \times 1\ m$ square
$S_3$	Discontinuities where the flaw echo has an amplitude greater than the characteristic curve $\varnothing 8\ mm$	$N_3$ (between $\varnothing 5\ mm$ and $\varnothing 8\ mm$ )	10 in the most populated $1\ m \times 1\ m$ square


a) Dimensions of each discontinuity in the cluster in question (see 9.2).

Table 5 — Acceptance criteria for flat product edge zone testing

Class	Permissible individual discontinuity size		Minimum discontinuity dimension considered $L_{min}$ mm	Permissible number of discontinuities smaller than the maximum area $S_{max}$ and longer than $L_{min}$ per 1 m length
	Maximum Dimension $L_{max}$ mm	Maximum Area $S_{max}$ mm <sup>2</sup>		
E <sub>0</sub>	100	2 000	50	6
E <sub>1</sub>	50	1 000	25	5
E <sub>2</sub>	40	500	20	4
E <sub>3</sub>	30	100	15	3
E <sub>4</sub>	20	50	10	2

NOTE For product with thickness  $\geq 60$  mm, a counting of the discontinuities is carried out using the characteristics curves for the 11 mm, 8 mm and 5 mm diameters holes:

- E<sub>3</sub> number of discontinuities giving echos with an amplitude between characteristic curves for the 8 mm and 11 mm diameter holes : 3;
- E<sub>4</sub> number of discontinuities giving echos with an amplitude between characteristic curves for the 5 mm and 8 mm diameter holes : 2.

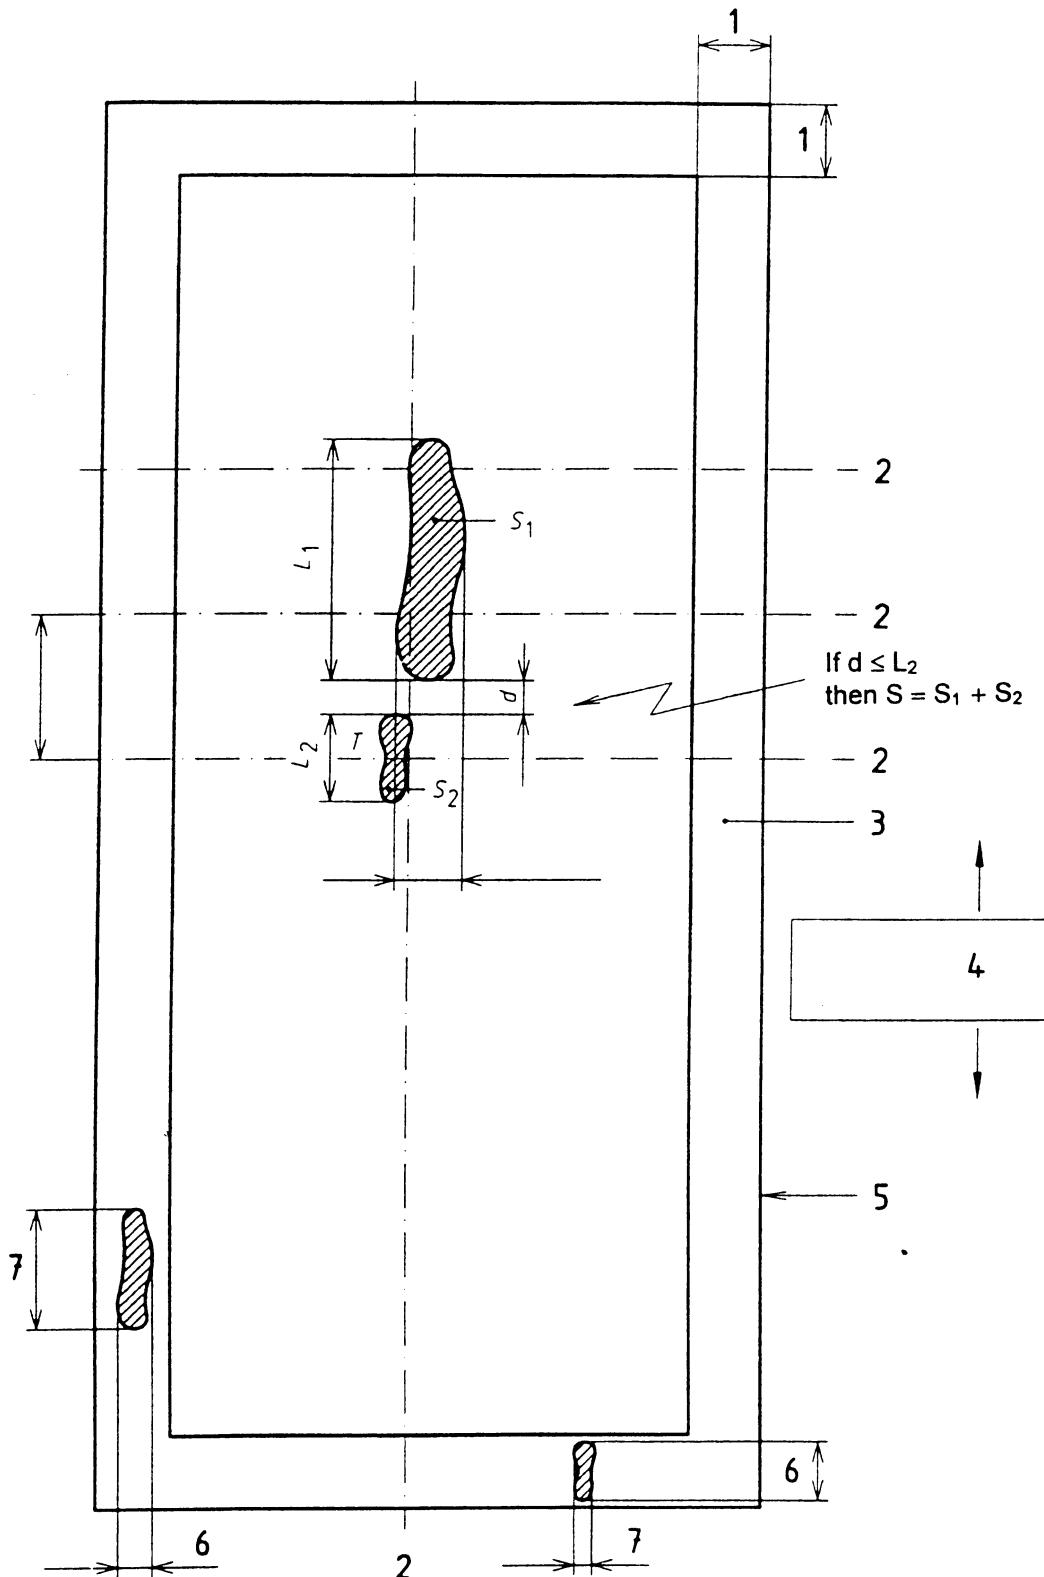

Key :

- 1 See Table 2 for the value of the edge zone width
- 2 Scan line
- 3 Edge zone
- 4 Principal rolling direction
- 5 Flat product
- 6 Width
- 7 Length

Figure 1 — Schematic representation of terms used

## Annex A

(informative)  
**List of equivalent terms in several European languages**

Table A.1

English	French	German	Italian	Dutch
Time base	Base de temps	Zeitablenkung	Base dei tempi	Tijdbasis
Noise signal	Bruit de fond	Rauschanzeige	Rumore di fondo	Ruis
Discontinuity echo	Echo d'anomalie	Fehlerecho	Eco del difetto	Indicatie-echo
Back echo	Echo de fond	Rückwandecho	Eco di fondo	Bodemecho
Probe	Traducteur	Prüfkopf	Sonda	Taster
Double transducer probe	Traducteur émetteur et récepteur séparés	SE-Prüfkopf	Sonda ed emettitore e ricevitore separati (sonda doppia)	Dubbel-kristaltaster
Single probe	Traducteur normal	Einschwinger-Prüfkopf	Sonda normale	Rechtetaster
Transducer	Transducteur	Schwinger	Transduttore	Kristal
Flat bottomed hole	Trou à fond plat	Flachbodenbohrung	Foro a fondo piatto	Vlakbodemgat
Dead zone	Zone morte	Tote Zone	Zona morta	Dode zone

*blank*

## BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

### **Revisions**

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover. Tel: 020 8996 9000. Fax: 020 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

### **Buying standards**

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: 020 8996 9001. Fax: 020 8996 7001.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

### **Information on standards**

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre. Tel: 020 8996 7111. Fax: 020 8996 7048.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration. Tel: 020 8996 7002. Fax: 020 8996 7001.

### **Copyright**

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

If permission is granted, the terms may include royalty payments or a licensing agreement. Details and advice can be obtained from the Copyright Manager. Tel: 020 8996 7070.